

Fasteners — Surface discontinuities —

Part 2: Nuts

The European Standard EN ISO 6157-2:2004 has the status of a
British Standard

ICS 21.060.20

National foreword

This British Standard is the official English language version of EN ISO 6157-2:2004. It is identical with ISO 6157-2:2004. It supersedes BS EN 493:1992 which is withdrawn.

The UK participation in its preparation was entrusted by Technical Committee FME/9, Bolts, nuts and accessories, to Subcommittee FME/9/1, Bolts, nuts, and accessories — Materials, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN ISO title page, the EN ISO foreword page, the ISO title page, the ISO foreword page, pages 1 to 10, the Annex ZA page and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 4 August 2004

© BSI 4 August 2004

ISBN 0 580 44213 6

English version

Fasteners - Surface discontinuities - Part 2: Nuts (ISO 6157-2:1995)

Eléments de fixation - Défauts de surface - Partie 2: Ecrous
(ISO 6157-2:1995)

Verbindungselemente - Oberflächenfehler - Teil 2: Muttern
(ISO 6157-2:1995)

This European Standard was approved by CEN on 1 July 2004.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Foreword

The text of ISO 6157-2:1995 has been prepared by Technical Committee ISO/TC 2 "Fasteners" of the International Organization for Standardization (ISO) and has been taken over as EN ISO 6157-2:2004 by Technical Committee CEN/TC 185 "Threaded and non-threaded mechanical fasteners and accessories", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2005, and conflicting national standards shall be withdrawn at the latest by January 2005.

This document supersedes EN 493:1992.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

Endorsement notice

The text of ISO 6157-2:1995 has been approved by CEN as EN ISO 6157-2:2004 without any modifications.

NOTE Normative references to International Standards are listed in annex ZA (normative).

INTERNATIONAL
STANDARD

ISO
6157-2

First edition
1995-08-01

Fasteners — Surface discontinuities —

Part 2:

Nuts

*Éléments de fixation — Défauts de surface —
Partie 2: Écrous*



Reference number
ISO 6157-2:1995(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 6157-2 was prepared by Technical Committee ISO/TC 2, *Fasteners*, Subcommittee SC 1, *Mechanical properties of fasteners*.

ISO 6157 consists of the following parts, under the general title *Fasteners — Surface discontinuities*:

- *Part 1: Bolts, screws and studs for general requirements*
- *Part 2: Nuts*
- *Part 3: Bolts, screws and studs for special requirements*

Fasteners — Surface discontinuities —

Part 2: Nuts

1 Scope

This part of ISO 6157 establishes limits for various types of surface discontinuities on nuts.

It applies to nuts with

- nominal thread diameters from 5 mm up to and including 39 mm;
- product grades A and B;
- all property classes according to ISO 898-2 and ISO 898-6, unless otherwise specified in product standards or agreed between supplier and purchaser.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 6157. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 6157 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 468:1982, *Surface roughness — Parameters, their values and general rules for specifying requirements.*

ISO 898-2:1992, *Mechanical properties of fasteners — Part 2: Nuts with specified proof load values — Coarse thread.*

ISO 898-6:1994, *Mechanical properties of fasteners — Part 6: Nuts with specified proof load values — Fine pitch thread.*

ISO 2320:1983, *Prevailing torque type steel hexagon nuts — Mechanical and performance properties.*

ISO 3269:1988, *Fasteners — Acceptance inspection.*

ISO 10484:—¹⁾, *Widening test on nuts.*

ISO 10485:1991, *Cone proof load test on nuts.*

1) To be published.

3 Types, causes, appearance and limits of surface discontinuities

Even if the permissible limits for surface discontinuities indicated in this clause occur, the minimum values for the mechanical and functional properties specified in ISO 898-2, ISO 898-6 and ISO 2320, as appropriate, shall still be met. In addition, the dimensional requirements of the appropriate product standard shall be satisfied.

NOTES

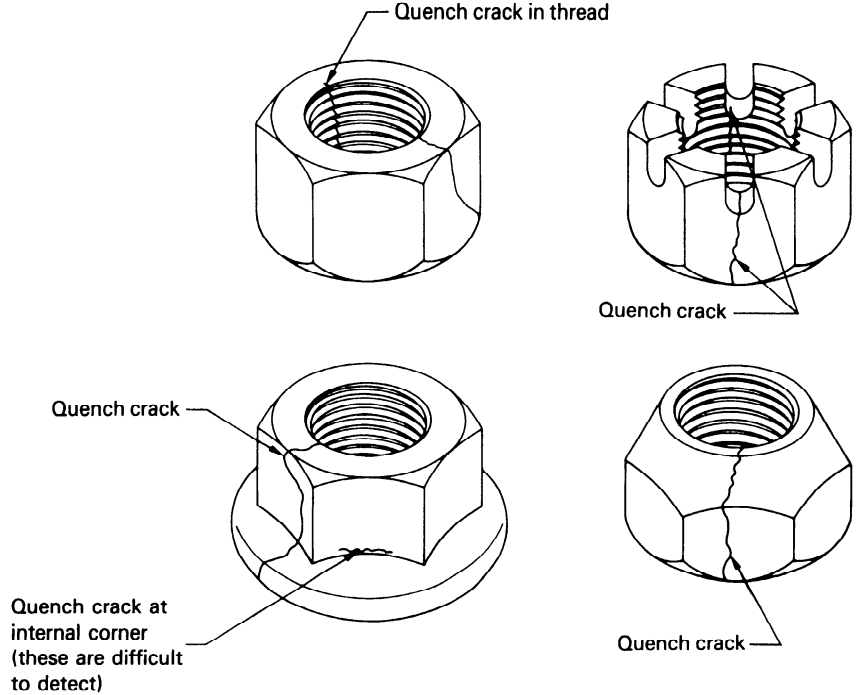
- 1 The figures in this clause are examples only; they also apply correspondingly to other types of nuts.
- 2 The individual figures show the surface discontinuities exaggerated in some cases for clarity.

3.1 Cracks

A crack is a clean (crystalline) fracture passing through or across the grain boundaries and may possibly follow inclusions of foreign elements. Cracks are normally caused by overstressing the metal during forging or other forming operations, or during heat treatment, or may have been present in the raw material.

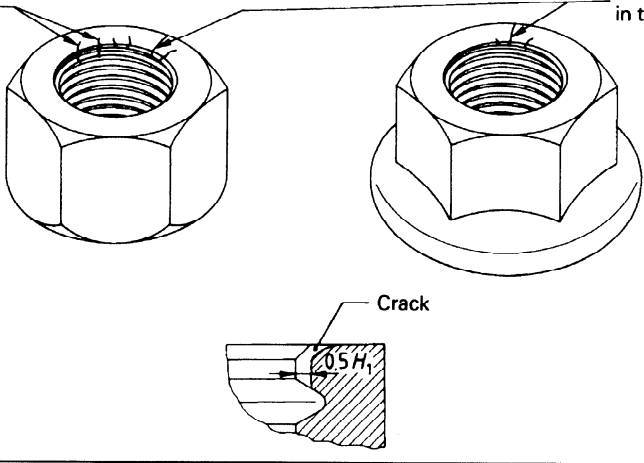
Where parts are subjected to significant reheating, cracks are usually discoloured by scale.

3.1.1 Quench cracks

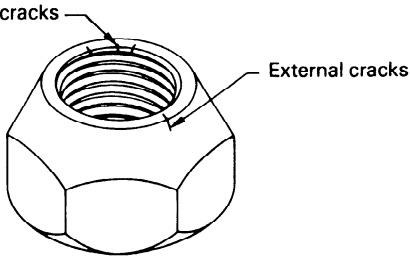
Cause	Quench cracks may occur during hardening due to excessively high thermal and transformation stresses. Quench cracks usually follow an irregular and erratic course on the surface of the nut.
Appearance	 <p>The diagrams illustrate various locations where quench cracks can occur on a hexagonal nut:</p> <ul style="list-style-type: none"> Quench crack in thread: A crack running through the threads of the nut. Quench crack: A crack on the side surface of the nut. Quench crack at internal corner (these are difficult to detect): A crack at the sharp internal corner where the threads meet the side surface. Quench crack: A crack on the top surface of the nut.
Limits	Quench cracks of any depth, any length, or in any location shall not be permitted.

Licensed copy: The University of Hong Kong, The University of Hong Kong, Version correct as of 27/11/2008 07:44, (C)

3.1.2 Forging cracks and inclusion cracks

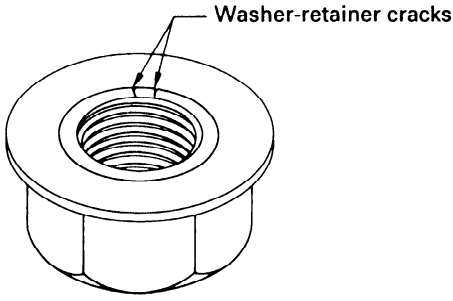
Cause	<p>Forging cracks may occur during the cut-off or forging operations and are located only in the top and bottom face of the nuts or in the intersection of the face and flat.</p> <p>Inclusion cracks are caused by non-metallic inclusions inherent in the raw material.</p>
Appearance	<p>Cracks in top or bottom face, or in thread, caused by inclusions</p>  <p>Forging cracks in top or bottom face</p> <p>Crack</p> <p>0,05d</p>
Limits	<p>Cracks located in the top and bottom faces shall be permitted, provided that:</p> <ul style="list-style-type: none"> — there are not more than two forging cracks which extend across the full width of the bearing face, neither of which shall exceed a depth of $0,05d$; — no crack extends into the tapped hole beyond the first full thread; — no crack in the first full thread exceeds a depth of $0,5H_1$; <p>where</p> <p>d is the nominal thread diameter;</p> <p>d_w is the diameter of the bearing face;</p> <p>H_1 is the effective thread height</p> $H_1 = 0,541P$ <p>where P is the pitch of the thread;</p> <p>s is the width across flats.</p> <p>In the case of nuts with a flange, cracks in the area between s and d_w shall not be permitted.</p>

3.1.3 Cracks in the locking element of all-metal prevailing torque type nuts

Cause	Cracks in the locking element of all-metal prevailing torque type nuts may occur during the cut-off, forging or deflecting process, and are either on the external or internal face.
Appearance	
Limits	<p>Cracks in the locking element resulting from the forging process shall be permitted, provided that all mechanical and functional requirements are met and that</p> <ul style="list-style-type: none"> — there are not more than two cracks which extend the full width of the crown circle, neither of which shall exceed a depth of $0,05d$; — no crack extends into the tapped hole beyond the first full thread; — no crack in the first full thread exceeds a depth of $0,5H_1$; <p>where</p> <p>d is the nominal thread diameter;</p> <p>H_1 is as defined in 3.1.2.</p> <p>Cracks in the locking element resulting from the deflecting process shall not be permitted.</p>

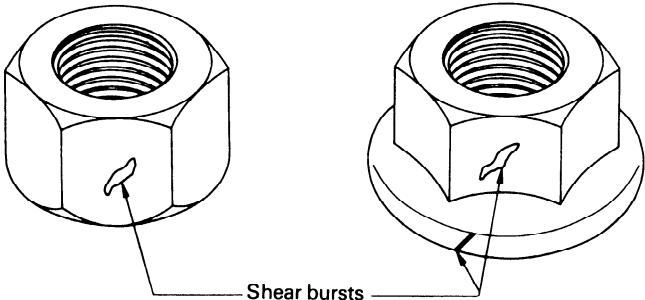
3.1.4 Cracks in the washer retainer of nuts with captive washers

A crack in the washer retainer is an opening in a lip or hub of metal used for securing a washer on a nut.

Cause	Washer-retainer cracks may occur when pressure is applied to the lip or hub during assembly of the washer.
Appearance	
Limits	Washer-retainer cracks are permissible if limited to the contour of the lip or hub used for retaining purposes, provided that the washer is securely held and able to rotate freely.

3.2 Shear bursts

Shear bursts are open breaks in the surface of the metal.

Cause	Shear bursts occur, for example, during forging operations on the external surfaces of nuts and at the periphery of nuts with a flange. Shear bursts are located in a plane with an orientation of approximately 45° to the axis of the nut.
Appearance	
Limits	<p>No shear burst in the flats of hexagon nuts shall extend into the bearing faces of a nut or the crown circle of a nut with a flange. Shear bursts occurring at the intersection of two wrenching flats shall not reduce the width across corners below the specified minimum value.</p> <p>Shear bursts at the periphery of the flange of nuts with a flange are allowed, providing they do not extend into the minimum diameter of the bearing face, d_w.</p>

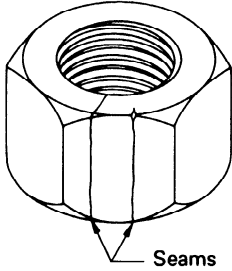
3.3 Bursts

Bursts are open breaks in the surface of the metal.

<p>Cause</p>	<p>Bursts may occur, for example, during forging operations on the external surfaces of nuts and at the periphery of nuts with a flange because of surface discontinuities in the raw material.</p>
<p>Appearance</p>	<p>The image contains three technical drawings of nuts, each with a line pointing to a surface defect labeled 'Burst'. 1. Top-left: A hex nut with a burst on its side face. 2. Top-right: A hex nut with a flange, showing a burst on the side face. 3. Bottom-center: A hex nut with a flange, showing a burst on the side face from a different perspective.</p>
<p>Limits</p>	<p>If a burst occurs in connection with a seam resulting from the raw material, the seam may extend into the crown circle (see 3.4) but not the burst.</p> <p>Bursts occurring at the intersection of two wrenching flats shall not reduce the width across corners below the specified minimum value.</p> <p>No burst or shear burst located at the intersection of the top or bottom face with a wrenching flat shall have a width greater than $(0,25 + 0,02s)$ mm, where s is the width across flats.</p> <p>Bursts and shear bursts at the periphery of the flange of nuts with a flange are allowed, provided that they do not extend into the minimum diameter of the bearing face, d_{wv}, and that the width of the burst does not exceed $0,08d_c$, where d_c is the flange diameter.</p>

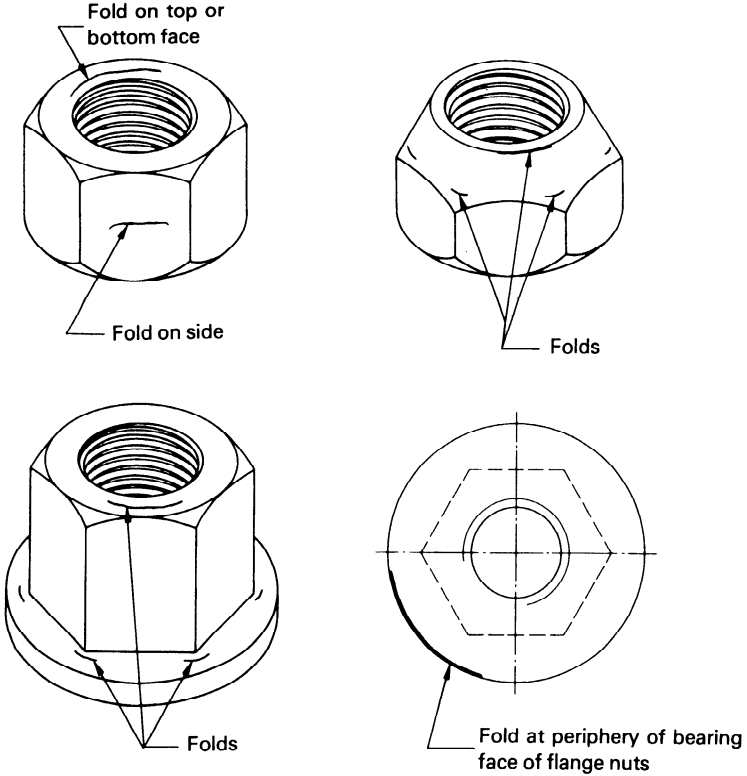
3.4 Seams

A seam is a longitudinal surface discontinuity in the form of an unwelded open fold in the material.

Cause	Seams are usually inherent in the raw material from which fasteners are made.
Appearance	
Limits	Seams shall be permitted, provided that a depth from the surface of $0,05d$ for all thread sizes is not exceeded, where d is the nominal thread diameter.

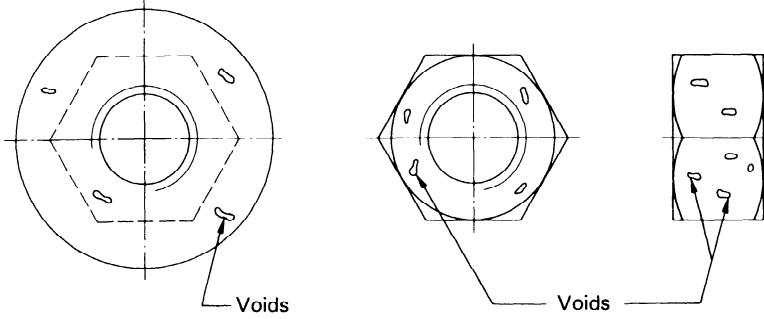
3.5 Folds

A fold is a doubling over of metal which occurs at the surface of the nut during forging.

Cause	Folds may be produced by material displacements during forging operations on nuts at or near the intersection of diameter changes, or on the top or bottom face of the nut.
Appearance	
Limits	Folds are permitted, but those located at the intersection of the flange periphery and bearing face of nuts with a flange shall not intrude into the bearing surface.

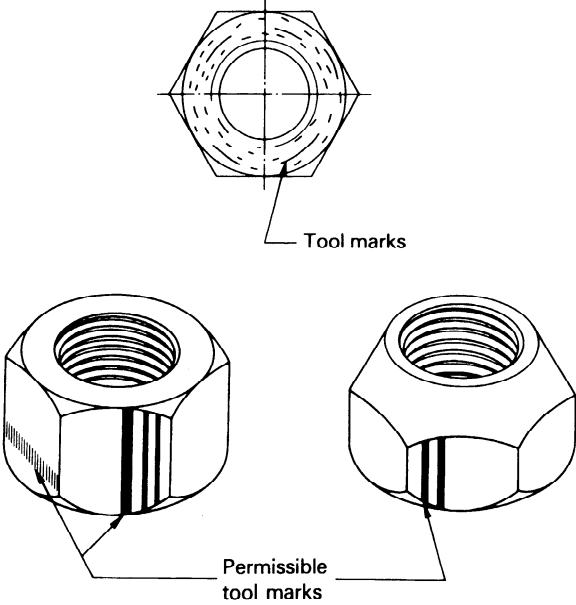
3.6 Voids

A void is a shallow pocket or hollow on the surface of a nut caused by non-filling of metal during forging or upsetting.

Cause	Voids are produced by marks or impressions of chips (shear burrs) or by rust formation on the raw material. They are not planished during forging or upsetting operations.
Appearance	
Limits	Depth, h , of voids: $h \leq 0,02d$ but with 0,25 mm max. where d is the nominal thread diameter. Area of all voids: The combined surface area of all voids on the bearing face shall not exceed 5 % of the bearing surface, for nuts with nominal thread diameter $d \leq 24$ mm 10 % of the bearing surface, for nuts with nominal thread diameter $d > 24$ mm.

3.7 Tool marks

Tool marks are longitudinal or circumferential grooves of shallow depth.

Cause	Tool marks are produced by relative motions between the work piece and the manufacturing tool.
Appearance	<p>Tool marks are most frequently elongated or circumferential.</p> 
Limits	Tool marks on the bearing surface shall not exceed a surface roughness of $R_a = 3,2 \mu\text{m}$ when tested in accordance with ISO 468. Tool marks on other surfaces are allowed.

3.8 Damages

Damages are indentations of any surface of a nut.

Cause	Damages, for example dents, scrapes, nicks and gouges, are produced by external actions during handling and transport.
Appearance	Damages have no precise geometrical shape, location or direction; they are identifiable as external action.
Limits	<p>Damages as described above shall not cause rejection unless it can be shown that they impair usability. (See also the requirements given at the beginning of clause 3.)</p> <p>If necessary, special packing and handling procedures may be used in order to avoid unacceptable damage during transport.</p>

4 Inspection and evaluation procedure

Sampling shall be carried out in accordance with ISO 3269, using the following procedures.

4.1 Routine acceptance inspection

For routine acceptance purposes, visual inspection procedures may be used to ensure that products conform to this part of ISO 6157.

4.2 Non-destructive testing

A representative sample shall be taken from the lot in accordance with ISO 3269 and subject to either $\times 10$ magnification visual examination tests or other suitable tests, for example magnetic techniques or eddy current. If no unacceptable surface discontinuity is found, the lot shall be accepted. If a user requires 100 % examination, this shall be stated at the time of ordering.

4.3 Destructive testing

If, after removing the surface coating, surface discontinuities are found which are likely to exceed the allowable limits, parts with the most severe surface discontinuities shall be selected for destructive testing (see ISO 10484 and ISO 10485).

4.4 Referee test

For referee purposes, nuts shall satisfy the widening test in accordance with ISO 10484. The cone proof load test in accordance with ISO 10485 may be applied in addition to the widening test, on agreement between the manufacturer and user.

4.5 Evaluation

If on visual inspection any product is found with quench cracks or deflection cracks in the locking element, or discontinuities which exceed the dimensional limits, the lot shall be subject to rejection.

If any part fails the appropriate destructive tests specified in 4.3 and 4.4, the lot shall be subject to rejection.

Annex ZA (normative)

Normative references to international publications with their relevant European publications

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

NOTE Where an International Publication has been modified by common modifications, indicated by (mod.), the relevant EN/HD applies.

<u>Publication</u>	<u>Year</u>	<u>Title</u>	<u>EN</u>	<u>Year</u>
ISO 898-2	1992	Mechanical properties of fasteners - Part 2: Nuts with specified proof load values - Coarse thread	EN 20898-2	1993
ISO 2320	1997	Prevailing torque type steel hexagon nuts - Mechanical and performance requirements	EN ISO 2320	1997
ISO 3269	2000	Fasteners - Acceptance inspection	EN ISO 3269	2000

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.

Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.
Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.
Email: copyright@bsi-global.com.